

Superconducting Gap vs. Wave Vector: Evidence for Hot Regions on the Fermi Surface

R. Gatt, S. Christensen, B. Frazer, Y. Hirai, T. Schmauder, R. J. Kelley, M. Onellion

Physics Department, University of Wisconsin-Madison, 1150 University Avenue, Madison, WI

53706

I. Vobornik, L. Perfetti, G. Margaritondo

Institut de Physique Appliquée, École Polytechnique Fédérale Lausanne, CH-1015 Lausanne,

Switzerland

A. Morawski, T. Lada, A. Paszewin

High Pressure Research Center Unipress, Polish Academy of Sciences, Warsaw, Poland

C. Kendziora

Naval Research Laboratory, Washington, D.C. 20011, USA

Abstract

We have used angular resolved photoemission to measure the angular dependence of the superconducting gap in highly overdoped Bi2212 ($T_c=65\text{K}$). While the node at 45 degrees is conserved, we find substantial deviation from a first order d-wave dependence away from the node. The pairing susceptibility is peaked at special regions on the Fermi surface. Comparing these results with a detailed mapping of the Fermi surface we performed, we could measure the extension and location of these hot regions. We find the hot regions to be evenly spread about the nominal locations of hot spots. The decrease of the gap amplitude away from these hot regions follows very closely theoretical calculations within the spin fluctuation approach. These

results strongly suggest that the pairing susceptibility is peaked at $Q = (\pi, \pi)$.

1. Text

The mechanism of high temperature superconductivity is one of the most important current problems of condensed matter physics, and a detailed description of the interaction which leads to pairing is still lacking. In common with most metals, the cuprate normal state exhibits a Fermi surface¹. Phase sensitive experiments,^{2,3} indicate that the superconducting gap (the order parameter of this second order phase transition) exhibits a change of sign around the Fermi surface. The most popular such unconventional order parameter (symmetry different from the crystal lattice) is a "simple d-wave," in which the gap varies with angle around the Fermi surface as $\Delta(\Phi) = \Delta(0) \cos(2\Phi)$. Here $\Phi = 45^\circ$ corresponds to the (π, π) direction in reciprocal space. Such an angular dependence is observed on optimally doped samples^{4,5}. Here we report on $\Delta(\Phi)$ measurements on highly overdoped samples. Our main result is that the gap versus angle data deviate from a simple d-wave order parameter. Combined with a detailed mapping of the Fermi surface, these results indicate that particular regions ("hot regions") of the Fermi surface show very high pairing susceptibility. This in turn provides insight into the superconducting pairing mechanism.

A general discussion on the electronic structure of the cuprates was given by Shen and Schrieffer⁶. They have stressed the difference in the line shape and doping dependence of the spectral function along the $\Gamma - M$ direction (parallel to the Cu-O bond) vs. along the $\Gamma - Y$ direction (parallel to the Cu-Cu direction). They suggested that such behavior could arise from electronic scattering peaked at $Q = (\pi, \pi)$. They further suggested this scattering mechanism to evolve into pairing susceptibility peaked at $Q = (\pi, \pi)$ at low temperatures. In this work, we provide evidence for such a behavior.

A feature observed in the underdoped cuprates is the pseudo-gap^{7,8} which manifests itself as a reduction of the spectral intensity at the Fermi level and a shift of spectral weight to higher frequencies. Its origin is believed to be related to incoherent pairing susceptibility existing

above T_c ^{9,10}. The value of the pseudo-gap decreases monotonically with temperature and continuously transforms into the value of the superconducting gap. This makes it difficult to distinguish between the true superconducting gap and the pseudo-gap¹¹. For high enough doping range there is no evidence of a pseudo-gap forming¹² and the leading edge gap closes at T_c .¹³ We therefore concentrate in our studies on the highly overdoped cuprates. Another advantage in studying the highly overdoped range is the general trend toward Fermi liquid behavior with increased doping¹⁴. This trend yields much sharper spectral features compared with the underdoped region. As a result we were able to reduce our error bars and detect fine details on which we report here.

In a recent work we reported the existence of a node in the gap amplitude in highly overdoped Bi2212 samples, consistent with a d-wave order parameter¹⁵. We found that to obtain results reproducible to gap sizes of 1meV, extreme care had to be taken to avoid even very small amounts of twinning or inter-growth in our crystals. Further, due to the angle-resolved photoemission system we used, we found that by using large, (typically $5 \times 5 \times 0.1 \text{ mm}^3$) single crystals, we reduced the background in our spectra enough to distinguish between very small and zero values of the gap. We attribute the earlier reports by some of us¹⁶ that the gap in the (π, π) direction is non-zero as due primarily to small amounts of material imperfections. The high quality of the crystals was needed to assure accurate alignment and to observe fine details such as superlattice bands. This last observation was important to assure measurements in the Y quadrant of the Brillouin zone, thus avoiding side effects rising from the Bi-O superlattice modulation¹⁷.

We used several experimental methods to characterize our samples, including polarized light microscopy, x-ray Laue diffraction, x-ray $\theta - 2\theta$ diffraction and scanning electron microscopy with Kikuchi pattern analysis. We extracted and characterized samples from batches grown by self flux methods¹⁸, using our previous experience in crystal growth and characterization¹⁹. To obtain overdoped (high carrier concentration) samples, we used two methods. In one, we annealed the crystals in an atmosphere of 20% oxygen and 80% argon

at a total pressure of 10 kbar. In the other, we sealed the samples in liquid oxygen and annealed them at 400C. Our data were obtained on the largest of these single crystals, up to $5 \times 5 \times 0.1 \text{ mm}^3$ in size. The value of T_c varied between 60-65K. The angle resolved measurements were performed using a Scienta hemispherical energy analyzer with a mean radius of 300 mm. The measured full-width half maximum energy resolution was 13-15 meV. The light source was a helium discharge lamp providing photons of 21.22 eV photon energy. The base pressure of the angle-resolved photoemission chamber was below 2×10^{-10} Torr and the sample was transferred from a load lock chamber, cooled to 11K, and a fresh surface exposed by cleaving the sample in situ. The low temperature assured us that the sample did not lose oxygen. The analyzer has a finite angular resolution of 4.5 deg , in terms of the angle (ϕ) with respect to the Y-M direction in reciprocal space.

Figure 1 is a comparison between the leading edge of the spectral function and the Fermi edge obtained from a freshly evaporated Ag film. In figure 1a, the two edges are coinciding, yielding a node in the superconducting gap within our sensitivity limit. Fig. 1b presents a gap of 1meV measured as the distance between the leading edge of the spectral function and the Fermi edge at the point of half maximum intensity. The figure demonstrates that the uncertainty in estimating the gap size is no more than ± 1 meV. Fig. 1c presents the gap at the $(0, \pi)$ point and Fig. 1d at $\phi = 15 \text{ deg}$. on the Fermi surface.

Fig. 2 presents the data collected on a total of 4 such crystals. The angular dependence of the superconducting gap with respect to the $(\pi, \pi) - (0, \pi)$ direction of the Brillouin zone is shown. The solid diamonds are measurements on the Fermi surface. The open diamonds are measurements away from the Fermi surface. The behavior close to the node follows very closely $\cos(2\phi)$ dependence, compatible with a simple, first order d-wave behavior, represented here by the dotted black line. There are important deviations from this dependence away from the node. It is seen clearly from the figure that the superconducting gap increases sharply in amplitude at special regions on the Fermi surface. Around 30 degrees, the gap amplitude increases sharply. This increase saturates around 22 degrees.

A major ingredient of the spin fluctuation approach^{20,21} to the problem of cuprate superconductivity is the existence of an interaction susceptibility peaked at a wave vector $Q = (\pi, \pi)$. This leads to special points on the Fermi surface (so called hot spots) which are connected by that displacement in k-space. To explore the possible connection between the angular dependence of the superconducting gap and the detailed shape of the Fermi surface, we present in Fig. 3 a detailed mapping of the Fermi surface for this high doping range. The mapping was done mainly at the Synchrotron Radiation Center in Wisconsin, and fine details were compared and completed in Lausanne. At Wisconsin we have used a VSW hemispherical electron energy analyzer with a total resolution of 35 meV. Recently we have repeated these measurements using a Scienta 200 energy analyzer on the PGM beamline at Wisconsin. We have measured cuts along high symmetry directions and more than 20 cuts along other directions, most of them in parallel to the $\Gamma - M$ direction. For obtaining the Fermi surface crossing points we have used the criteria developed by Ding et. al⁹. An example for such cuts is presented in the inset of figure 3.

Fig. 4 combines the results presented in figures 2 and 3. The nominal location of hot spots is given as the intersection of the dashed square with $Q = (\pi, \pi)$ as its side and the Fermi surface. As can be seen from Fig. 4 there are exactly eight such points on the Fermi surface (filled circles). These so called hot spots are the basis of numerous theoretical works within the spin fluctuation approach²² and there were several attempts to observe them experimentally^{23,24}. However It was shown that the features observed experimentally could be naturally described as a structural effect, a result of the superlattice modulation in Bi2212^{25,26}. The observation presented in Fig. 2 is a direct measurement of the true superconducting gap (and not of a pseudogap). It is seen clearly from the figure that the pairing susceptibility is peaked at isolated regions on the Fermi surface. By performing measurements in the Y quadrant of the Brillouin zone, we distinguish between the main band crossing and the side bands which are the result of the superlattice modulations. Our

measurement yields a value of $K_{co} = (0.95\pi/a, 0.12\pi)$, in polar units (ρ, ϕ) with respect to the Y point and the Y-M line, as a cutoff vector for this region of high pairing susceptibility on the Fermi surface. The construction of fig. 4 yields $K_{hs} = (0.96\pi/a, 0.06\pi)$ for our doping range. Notice that the measured K_{hs} falls exactly in the middle between K_{co} and the zone boundary. We emphasize that both K_{hs} and K_{co} are determined by the data of Figs. 2 and 3, rather than a theoretical assumption. Recently, Abanov et al. developed a new procedure for calculating T_c in the scenario where the pairing susceptibility is highly peaked at a hot spot²⁷. The solid line in Fig. 2 is a one parameter fit to their expression, describing the decrease in magnitude of the superconducting gap away from a hot spot. The fit yields a value of $0.9 \pm 0.1nm$ (about two unit cells) for the magnetic correlation length, which is as expected for this highly overdoped region of the phase diagram.

In conclusion, we measured the angular dependence of the superconducting gap. We found substantial variation from a first order d-wave behavior away from the node. We found that the pairing susceptibility is peaked at special regions on the Fermi surface. Using a detailed mapping of the Fermi surface for this doping range, we could measure the nominal hot spot location and the extension of our measured hot regions. We have found the hot regions to be evenly spread about the nominal locations of hot spots. The decrease of the gap amplitude away from these hot spots follows very closely theoretical calculations within the spin fluctuation approach. From a fit to these calculations we have extracted the magnetic correlation length and found it in excellent agreement with our highly overdoped range.

Note again, that the hot spots are not highly confined in k-space, but occupy considerable regions on the Fermi surface. This behavior can be described within the spin fluctuation approach as a result of the short magnetic correlation length in this doping range. Thus, as the magnetic correlation length decreases away from half filling, the pairing susceptibility acquires a finite broadness while still peaked at $Q = (\pi, \pi)$. Our results suggest that under-

doped samples should have less broadening, with the hot regions becoming hot spots.

Whatever is the pairing mechanism, our measurements show a high anisotropy in the angular dependence of the superconducting gap that is inconsistent with a simple d-wave picture (but still consistent with general B_{1g} symmetry). Our measurements show clearly a steep increase of the superconducting gap at hot regions on the Fermi surface implying their overall importance in inducing superconductivity. Both the sharp increase of the gap amplitude, and the measured range on the Fermi surface for which this increase is observed, suggest very strongly that the electronic scattering that is the precursor for pairing in the high temperature superconductors is peaked at $Q = (\pi, \pi)$.

ACKNOWLEDGEMENTS. We benefited from discussions with P. Chaudhari, S. Rast, A. Chubukov, M. Rzchowski, L. Forro, M. Grioni, A. Leggett, M. Weger, C.C. Tsuei, R. Joynt and I. Panas. Financial support was provided by the U.S. NSF and Fonds National Suisse.

CORRESPONDENCE should be addressed to R.G. (e-mail: Rafi@src.wisc.edu).

REFERENCES

1. Z.-X. Shen and D. S. Dessau, Physics Reports **253**, 1 (1994) and references therein.
2. D. A. Wollman et. al., Phys. Rev. Lett. **71**, 2134 (1993).
3. C.C. Tsuei et. al., Nature **387**, 481 (1997).
4. Z. -X. Shen et. al., Phys. Rev. Lett. **70**, 1553 (1993).
5. H. Ding et. al., Phys. Rev. B **54**, 9678 (1996).
6. Z.-X. Shen and J. R. Schrieffer, Phys. Rev. Lett., **78**, 1771 (1997).
7. H. Ding et. al., Nature **382**, 51 (1996)
8. J. M. Harris et. al., Phys. Rev. Lett., **79**, 143 (1997)
9. H. Ding et. al., Phys. Rev. Lett., **78**, 2628 (1997)
10. A. V. Chubukov, Europhys. Lett., **44**, 655 (1998)
11. K. Gorny et. al., Phys. Rev. Lett., **82**, 177 (1999).
12. J. L. Tallon et. al., Phys. Rev. Lett., **75**, 4114 (1995)
13. A. G. Loeser et. al., Science, **273**, 325 (1996)
14. S. Misra et. al., Phys. Rev. B **58**, R8905 (1998)
15. R. Gatt et. al., preprint.
16. R. J. Kelley et.al., Science **271** 1255 (1996).
17. M. R. Norman et. al., Phys. Rev. B **52** 15107(1995).
18. P. D. Han and D. A. Payne, J. Cryst. Growth **104**, 201 (1990).
19. R. Gatt et.al., Physica C **276**, 270 (1997).
20. T. Moriya et al., J. Phys. Soc. Japan **59**, 2905 (1990)

- 21. P. Monthoux et al., Phys. Rev. B **46**, 14803 (1992)
- 22. M. H. Sharifzadeh Amin et. al., Phys. Rev. Lett., **77**, 3017 (1996).
- 23. P. Aebi et al., Phys. Rev. Lett., **72**, 2757 (1994).
- 24. N. L. Saini et al., Phys. Rev. Lett., **79**, 3467 (1997).
- 25. H. Ding et. al., Phys. Rev. Lett., **76**, 1533 (1996).
- 26. J. Mesot et. al., Phys. Rev. Lett., **82**, 2618 (1999).
- 27. A. Abanov, A. Chubukov, A. Finkelstein, preprint; University of Wisconsin Report UW/PH/006-257 (1999).

FIGURES


Fig. 1. The superconducting gap as extracted from the difference between the leading edge of the spectral function and the Fermi edge obtained from the spectrum of a freshly evaporated Ag film. (a) zero gap value, the two edges are coinciding, (b) 1meV gap value, as extracted from the difference of the two spectra at the point of half maximum intensity. The inset shows the extended energy scale in both figures. (c), (d) The shift of the leading edge at the $(0, \pi)$ point and the point c on the Fermi surface as indicated by the inset in both figures.

Fig. 2. The angular dependence of the superconducting gap in highly overdoped ($T_c=65K$) Bi2212. The dashed line is a fit to a first order d-wave gap ($\cos 2\theta$). The solid line marked ACF is a fit to Abanov et. al. expression for the decrease in the gap value away from a hot spot.


Fig. 3. The Fermi surface of highly overdoped Bi2212. Open circles: measurement points. Filled circles: main Fermi surface crossing points. Gray diamonds: superlattice band crossing points. Open squares were obtained by symmetry operations. The solid line is a smooth fit to the data, used in figure 4. Inset: Energy dispersive curves close to the main Fermi surface crossing points along directions a and b as indicated in the figure. Both directions are perpendicular to $\Gamma - M$ direction.

Fig. 4. The location of hot regions on the Fermi surface. These regions of high gap amplitude are extended from the zone boundary up to K_{co} , the cutoff vector for which the gap amplitude falls sharply to a first order d-wave value. K_{hs} are the locations of nominal hot spots, obtained from the intersection of the Fermi surface and the square with $Q = (\pi, \pi)$ as its side. Note that K_{hs} falls exactly in the center of the hot region.


Gatt et al., Fig. 1a

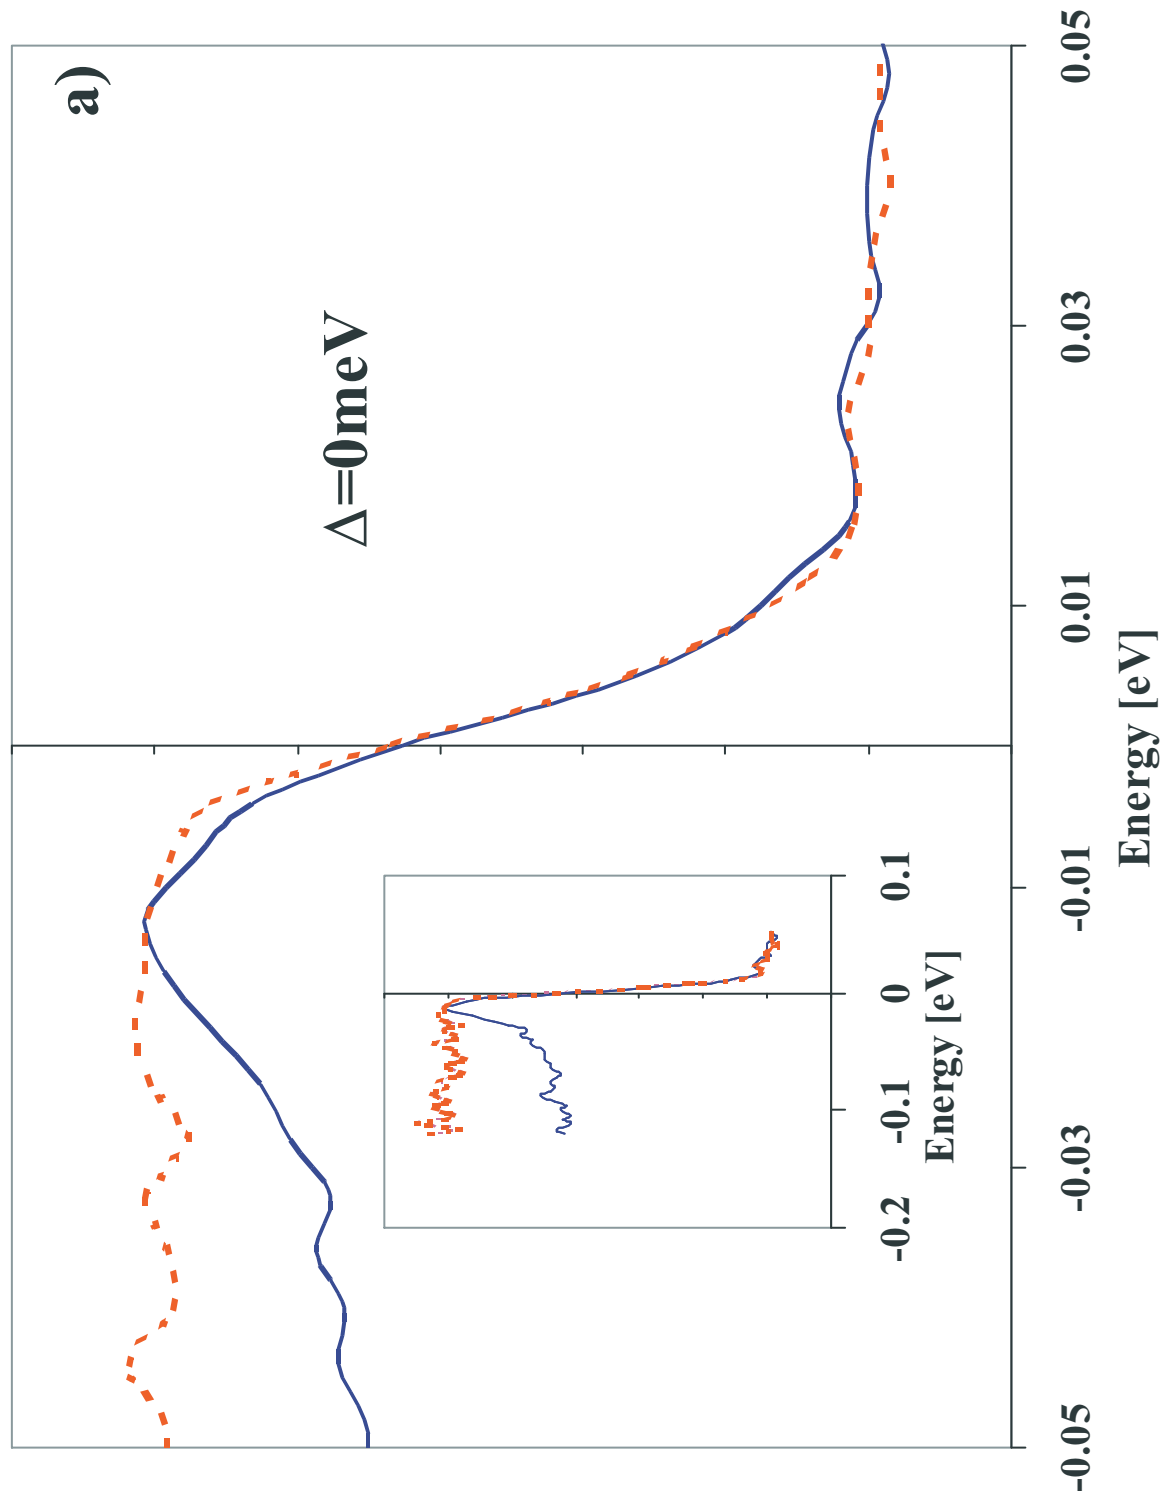


Gatt et al., Fig. 1b

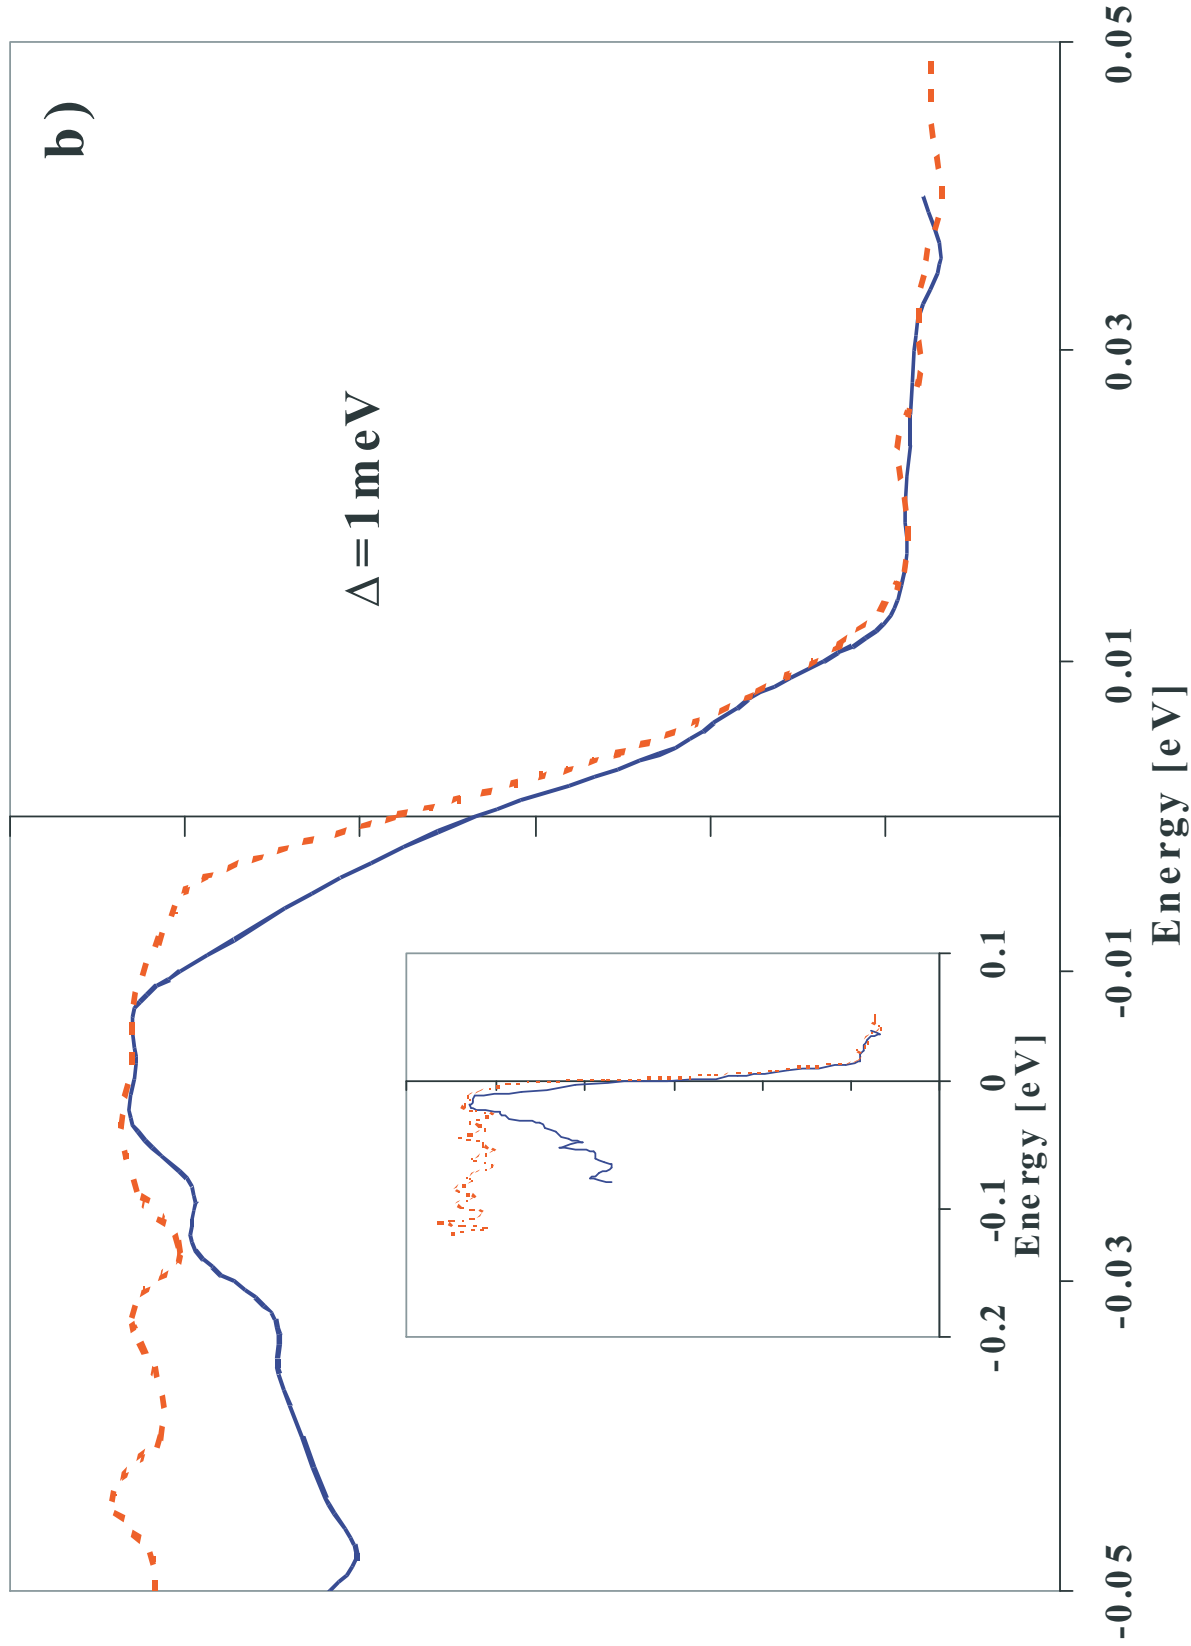


Gatt et al., Fig. 1c

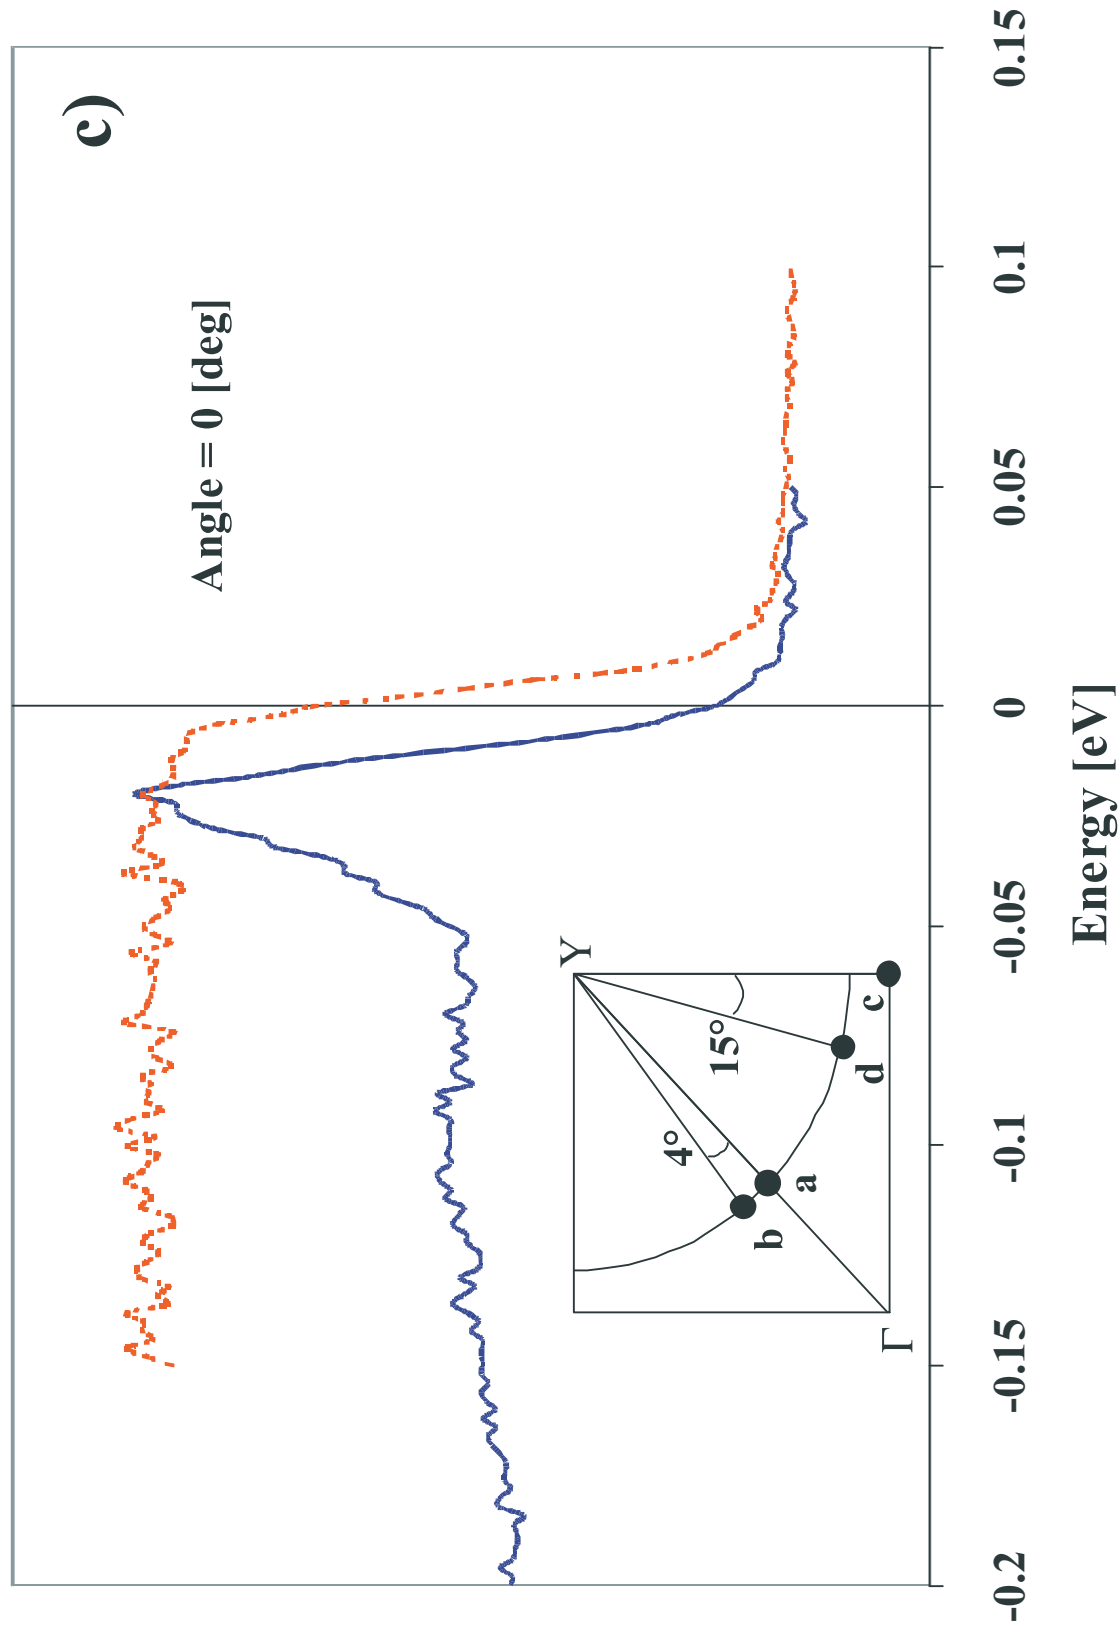


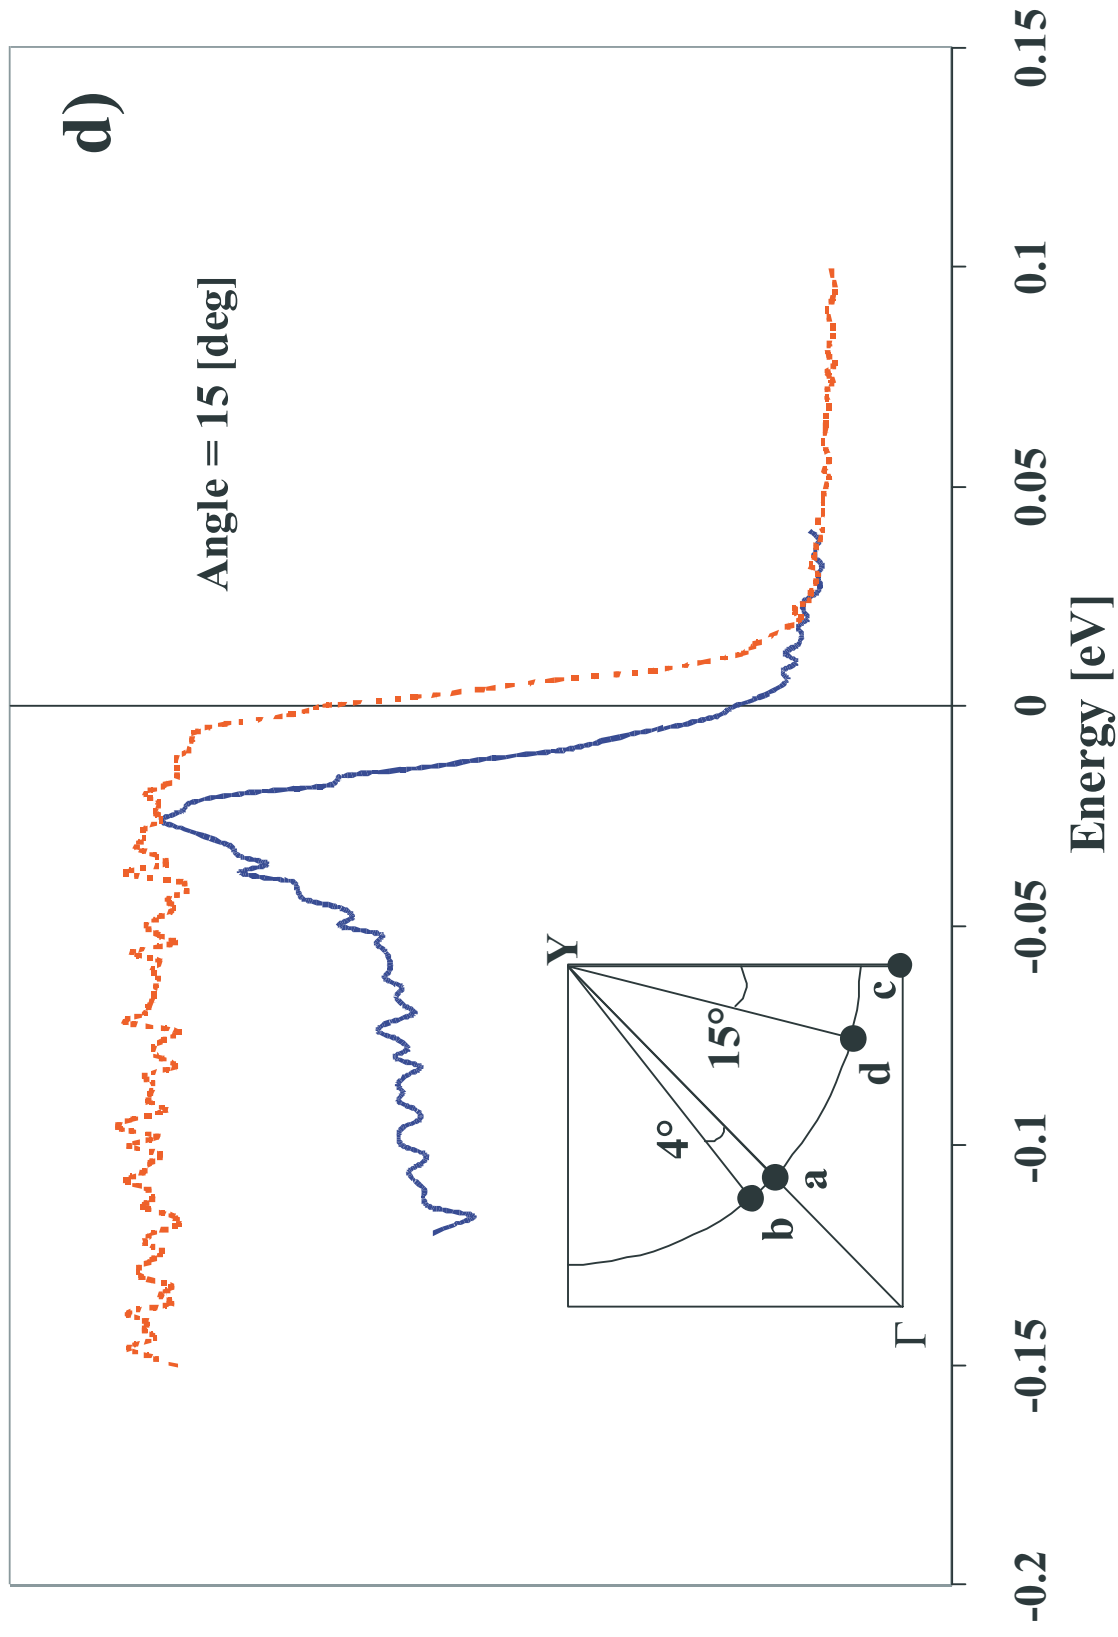

Gatt et al., Fig. 2

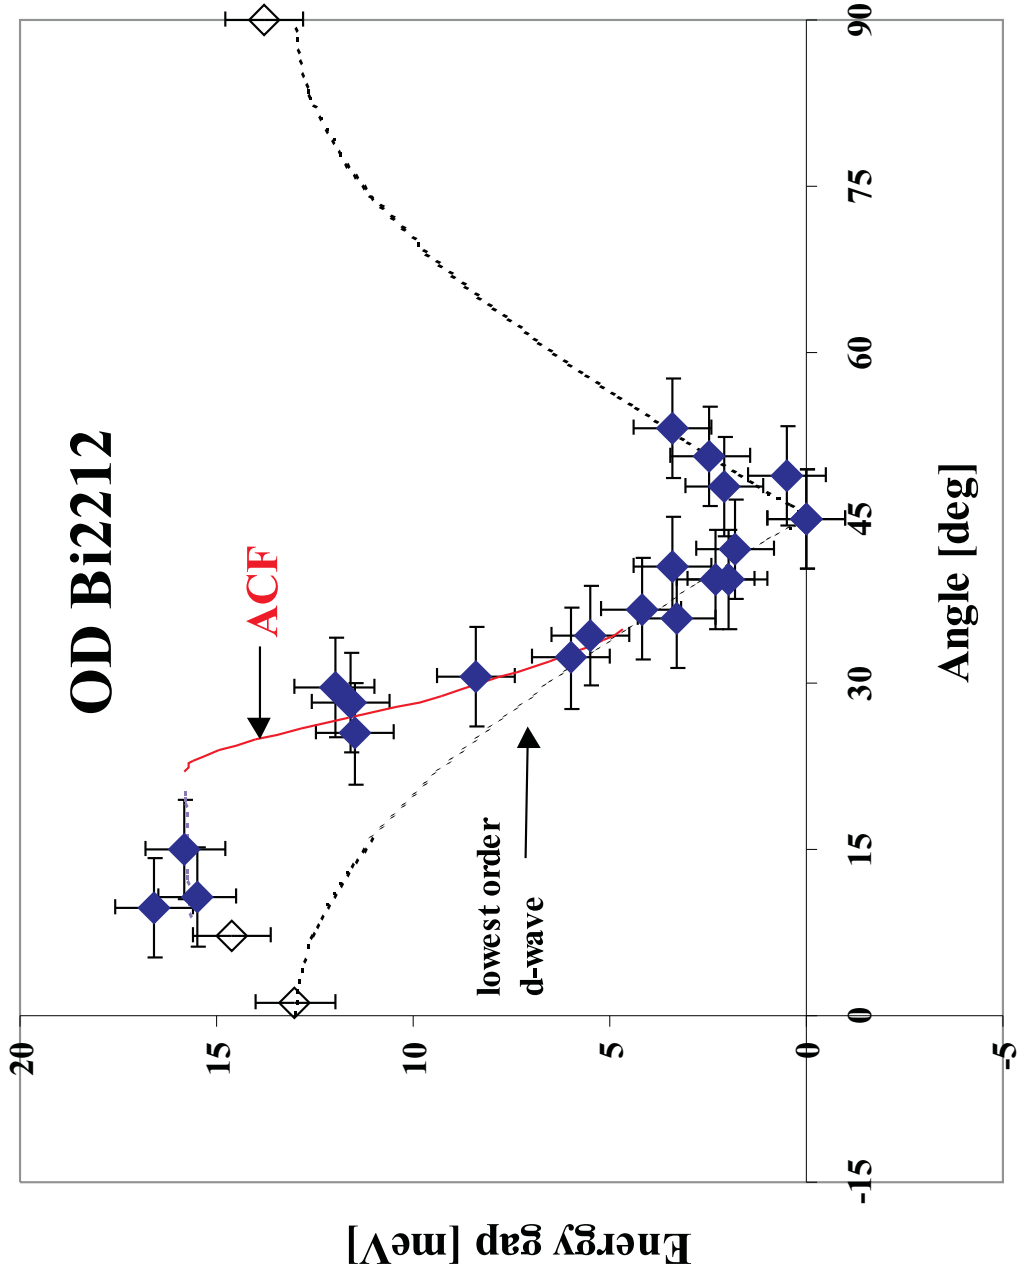

Gatt et al., Fig. 3

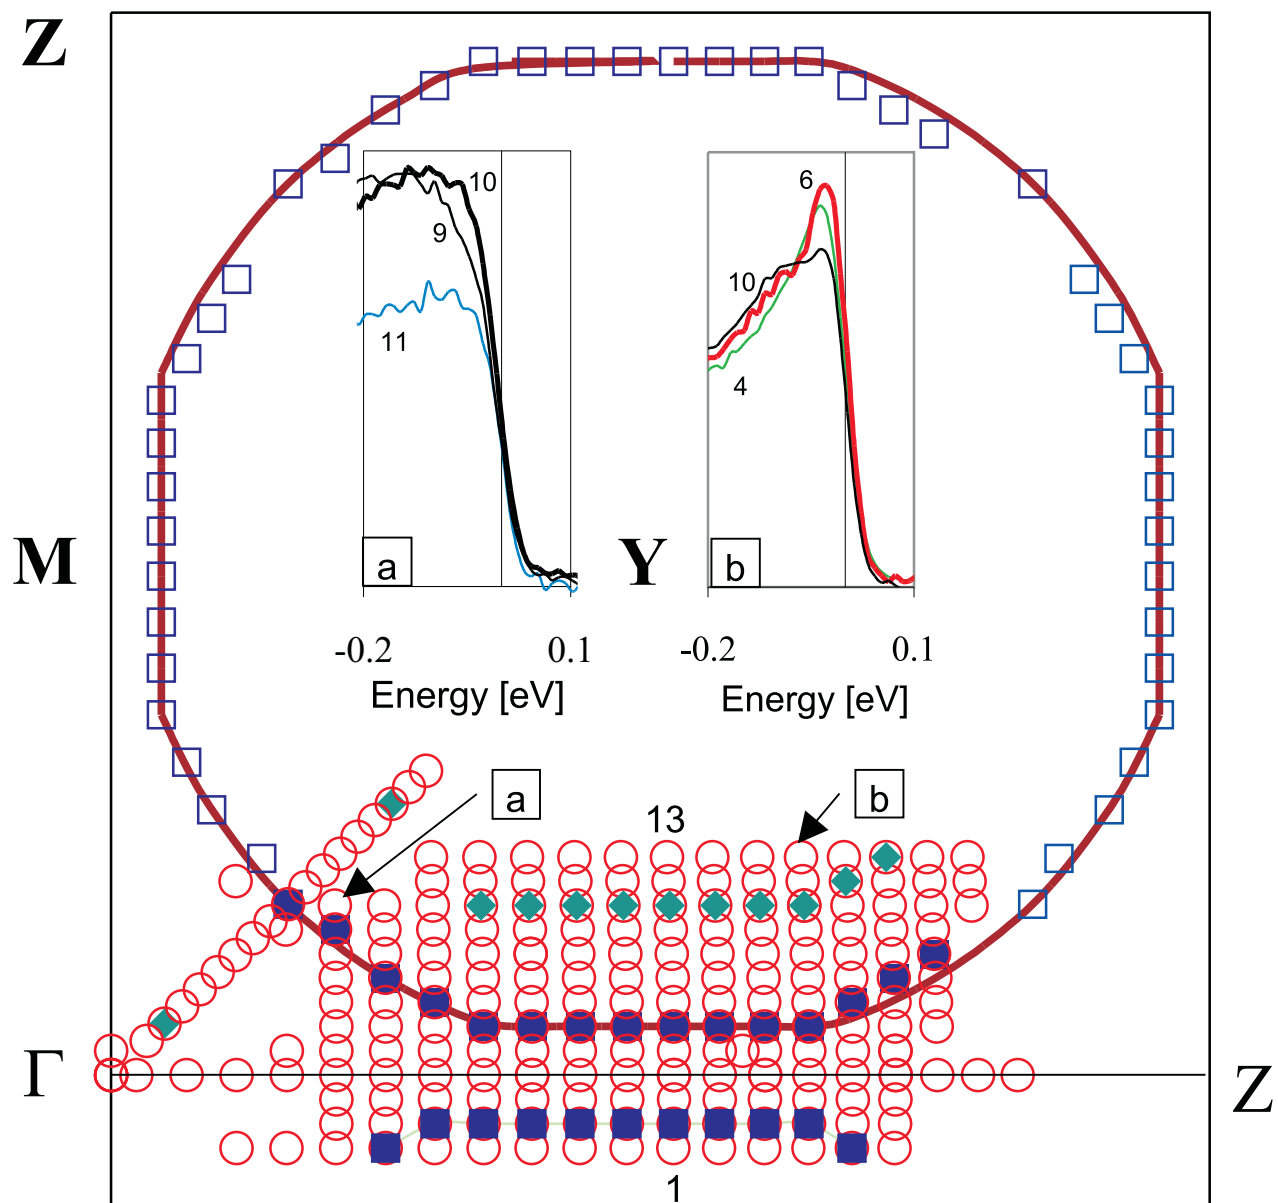

Gatt et al., Fig. 4

